

Understanding the Potential and Limitations of Dilute Nitride Alloys for Solar Cells

S. Kurtz, A. Ptak, S. Johnston, C. Kramer,
M. Young, D. Friedman, J. Geisz, W. McMahon,
A. Kibbler, J. Olson, R. Crandall, and H. Branz

*Presented at the 2005 DOE Solar Energy Technologies
Program Review Meeting
November 7–10, 2005
Denver, Colorado*

Conference Paper
NREL/CP-520-38998
November 2005

NREL is operated by Midwest Research Institute • Battelle Contract No. DE-AC36-99-GO10337



NOTICE

The submitted manuscript has been offered by an employee of the Midwest Research Institute (MRI), a contractor of the US Government under Contract No. DE-AC36-99GO10337. Accordingly, the US Government and MRI retain a nonexclusive royalty-free license to publish or reproduce the published form of this contribution, or allow others to do so, for US Government purposes.

This report was prepared as an account of work sponsored by an agency of the United States government. Neither the United States government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States government or any agency thereof.

Available electronically at <http://www.osti.gov/bridge>

Available for a processing fee to U.S. Department of Energy
and its contractors, in paper, from:

U.S. Department of Energy
Office of Scientific and Technical Information
P.O. Box 62
Oak Ridge, TN 37831-0062
phone: 865.576.8401
fax: 865.576.5728
email: <mailto:reports@adonis.osti.gov>

Available for sale to the public, in paper, from:

U.S. Department of Commerce
National Technical Information Service
5285 Port Royal Road
Springfield, VA 22161
phone: 800.553.6847
fax: 703.605.6900
email: orders@ntis.fedworld.gov
online ordering: <http://www.ntis.gov/ordering.htm>



Printed on paper containing at least 50% wastepaper, including 20% postconsumer waste

Understanding the Potential and Limitations of Dilute Nitride Alloys for Solar Cells

Sarah Kurtz, Aaron Ptak, Steve Johnston, Charlene Kramer, Michelle Young, Daniel Friedman, John Geisz, William McMahon, Alan Kibbler, Jerry Olson, Richard Crandall, and Howard Branz
National Renewable Energy Laboratory, Golden, Colorado, sarah_kurtz@nrel.gov

ABSTRACT

Dilute nitride alloys provide a powerful tool for engineering the band gap and lattice constant of III-V alloys. However, nitrogen degrades the performance of GaAs solar cells. This project seeks to understand and demonstrate the limits of performance of GaInNAs alloys by (a) correlating deep-level transient spectroscopy (DLTS) data with device performance and (b) using molecular beam epitaxy (MBE) to reduce background impurity concentrations.

1. Objectives

The Solar Program seeks to develop technologies that can provide cost-effective electricity generation. One strategy to reduce cost is to use concentrating optics to focus the sunlight on small, high-efficiency solar cells. Multijunction solar cells have achieved the highest efficiency (39%) of any technology and have the theoretical potential to achieve efficiencies equivalent to or exceeding all other approaches. Dilute nitride materials have demonstrated a range of band gaps, providing a possible pathway to higher-efficiency multijunction cells. The objective of this project is to explore the potential and limitations of the dilute nitride alloys for solar cells, especially $\text{Ga}_{1-3x}\text{In}_{3x}\text{N}_x\text{As}_{1-x}$ with a band gap of 0.9-1.3 eV.

2. Technical Approach

2.1 Correlation of Device Performance with DLTS

DLTS measurements of GaInNAs alloys show numerous features, implying that these alloys contain many defects. Here, we reduce the complexity of the DLTS spectra and correlate the data with device performance to determine which of the DLTS features may be of importance.

2.2 Achievement of High-Photocurrent GaInNAs Cell

The minority-carrier diffusion lengths of p-type 1-eV GaInNAs are too short to measure, and, thus, cannot be optimized directly. Instead, GaInNAs solar cells are dominated by field-aided collection that is correlated with low background carrier concentration. GaInNAs grown using a p-i-n structure with wide depletion widths (usually) shows high photocurrents. We pursue MBE as a pathway to lower the background carrier concentrations and increase the photocurrent.

3. Results and Accomplishments

3.1 Correlation of DLTS Data and Device Performance

Although undoped dilute nitride solar cells usually outperform doped cells due to enhanced field-aided collection, the interpretation of DLTS spectra of p-i-n

cells is complicated. We observed that the DLTS spectra were greatly simplified by the use of doped active layers. Indeed, growth conditions were used that resulted in only one dominant feature in the DLTS spectra. GaAs-GaNAs junctions were studied to ensure that defects were observed on only one side of the junction.¹⁻⁵

The dark currents of GaAs/GaNAs n-p diodes (with p-type GaNAs active layers) correlated with the observation of an electron trap (Fig. 1). This correlation does not prove a causal relationship, but the decrease of the open-circuit voltage is semi-quantitatively explained by a reduction in the electron quasi-Fermi level by the electron trap (Fig. 2).¹

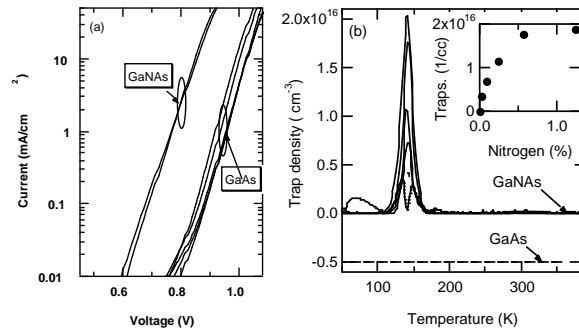


Fig. 1. (a) Dark I-V curves comparing $\text{GaN}_x\text{As}_{1-x}$ ($x < 0.1\%$) and GaAs diodes. (b) DLTS data for $\text{GaN}_x\text{As}_{1-x}$ samples with $x < 1.2\%$. The GaAs scans (dashed lines) are offset for clarity; the height of the peak for the $\text{GaN}_x\text{As}_{1-x}$ samples (indicating trap concentration) increased with x (see inset).¹

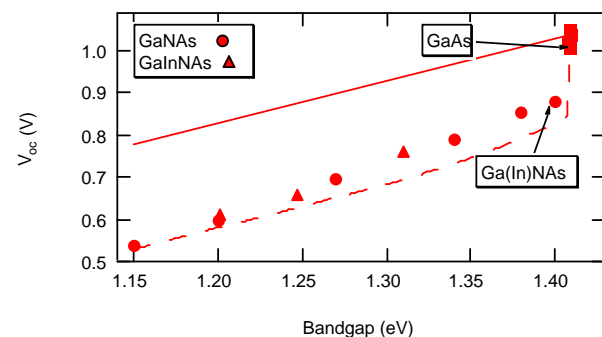


Fig. 2. Open-circuit voltage as a function of band gap for GaAs (squares) and Ga(In)NAs solar cells. The solid line shows the unity slope expected for the open-circuit voltage if it followed the band gap; the dashed line shows the semi-quantitative model.¹

The study of n-type GaAs/GaNAs diodes showed a similar electron trap.^{3,4} The concentration of electron traps was observed to increase with doping for both the p-type and n-type GaNAs. Much work remains to

prove the importance of the observed electron trap, identify its origin, and determine the extent to which its effects can be reduced.

3.2 High Photocurrent GaInNAs Solar Cells

The photocurrent of dilute-nitride solar cells correlates with the depletion width. Unfortunately, GaInNAs alloys grown by metal-organic chemical vapor deposition have high background carrier concentrations (and, hence, low depletion widths). In FY2004, we used MBE growth to demonstrate that wide depletion widths resulted in much higher photocurrents for dilute nitrides (Fig. 3),^{7,8} as expected from our analysis of the field-region collection.⁶

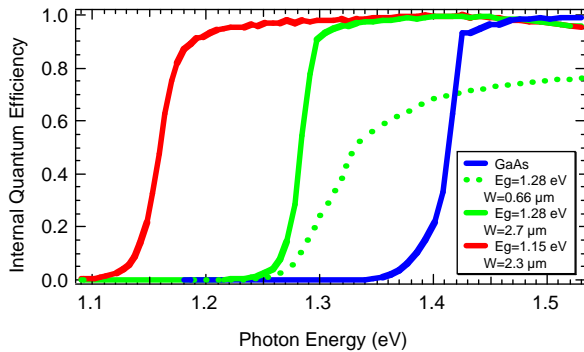


Fig. 3. Internal quantum efficiencies for MBE-grown GaNAs samples with different band gaps and depletion widths.⁸

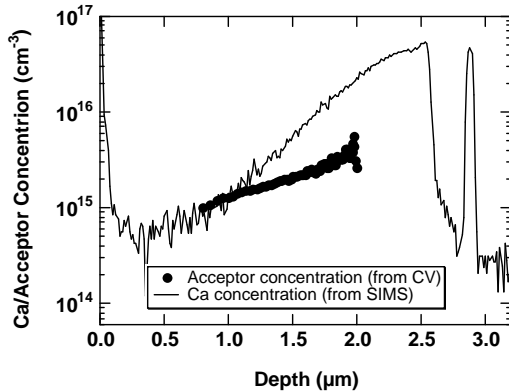


Fig. 4. Comparison of calcium concentration with net acceptor concentration for GaInNAs sample.⁹

It appears that the lower carbon and hydrogen concentrations associated with MBE growth allow the wide depletion widths to be obtained. However, the removal of carbon and hydrogen, though a necessary condition, is not sufficient to achieve the wide depletion widths. Other unintentional dopants and charged defects have the potential to reduce the depletion width. This year we discovered that calcium can be introduced into GaInNAs from surface contamination of the GaAs wafer.⁹ An example of the correlation between unintentional calcium incorporation and observed background acceptor concentration is shown in Fig. 4.

Further system modifications are needed to sufficiently control the growth process in order to consistently achieve wide depletion widths. Although we have not yet achieved the widest depletion widths for 1 eV alloys, we have reason to believe that high photocurrents are achievable.

Unfortunately, the cells that show high photocurrents do not show GaAs-like photovoltages. This may imply that the electron traps discussed earlier are not the only defect affecting the photovoltage in GaInNAs. If low carrier concentrations do indeed reduce the density of electron traps (without a corresponding increase in photovoltage), there must be more problems left to be uncovered. Thus, we conclude that high photocurrents are likely to be achieved, but it is unlikely that high photovoltages will ever be realized.

4. Conclusions

We observe electron traps in GaNAs alloys and correlate them with device performance. MBE growth serves to reduce the background doping to provide improved photocurrents as long as all contaminants, including calcium, are controlled.

ACKNOWLEDGEMENTS

We thank R. Reedy for SIMS measurements and S. Zhang and S. Wei for useful discussions. The work was performed under DOE contract DE-AC36-99-GO10337.

REFERENCES AND MAJOR FY 2005 PUBLICATIONS

- ¹S. Kurtz, S. Johnston, and H. M. Branz, "Capacitance-spectroscopy identification of a key defect in N-degraded GaInNAs solar cells" *Appl Phys Lett* **86**, 113506 (2005).
- ²S. W. Johnston, S. R. Kurtz, D. J. Friedman, et al., "Observed trapping of minority-carrier electrons in p-type GaAsN during deep-level transient spectroscopy measurement" *Appl Phys Lett* **86**, 072109 (2005).
- ³S. Kurtz, S. W. Johnston, J. F. Geisz, et al., "Effect of nitrogen concentration on the performance of Ga_xIn_{1-x}N_yAs_{1-y} solar cells" in *Proceedings of the 31st IEEE PVSC* (IEEE, Orlando, Florida, 2005), p. 595.
- ⁴S. Johnston, S. Kurtz, D. J. Friedman, et al., "Electron traps in p-type GaAsN characterized by deep-level transient spectroscopy" in *Proceedings of the 31st IEEE PVSC* (IEEE, Orlando, Florida, 2005), p. 599.
- ⁵S. Prasad, A. Khan, S. W. Johnston, et al., "Evolution of defect complexes in InGaAsN" in *Proceedings of the 31st IEEE PVSC* (IEEE, Orlando, Florida, 2005), p. 731.
- ⁶D. J. Friedman, A. J. Ptak, S. R. Kurtz, et al., "Analysis of depletion-region collection in GaInNAs solar cells" in *Proceedings of the 31st IEEE PVSCe* (IEEE, Orlando, Florida, 2005), p. 691.
- ⁷A. J. Ptak, D. J. Friedman, S. Kurtz, et al., *J. Appl. Phys.* in press.
- ⁸A. J. Ptak, D. J. Friedman, S. Kurtz, et al., "Enhanced-depletion-width GaInNAs solar cells grown by molecular-beam epitaxy" in *Proceedings of the 31st IEEE PVSC* (IEEE, Orlando, Florida, 2005), p. 603.
- ⁹A. J. Ptak, D. J. Friedman, S. Kurtz, et al., "Role of calcium impurities in enhanced-depletion-width GaInNAs solar cells grown by molecular-beam epitaxy" *J Vac Sci Technol B*, submitted 9/05 (2005).

REPORT DOCUMENTATION PAGE*Form Approved*
OMB No. 0704-0188

The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Department of Defense, Executive Services and Communications Directorate (0704-0188). Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.

PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ORGANIZATION.

1. REPORT DATE (DD-MM-YYYY) November 2005			2. REPORT TYPE Conference Paper		3. DATES COVERED (From - To)	
4. TITLE AND SUBTITLE Understanding the Potential and Limitations of Dilute Nitride Alloys for Solar Cells					5a. CONTRACT NUMBER DE-AC36-99-GO10337	
					5b. GRANT NUMBER	
					5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S) S. Kurtz, A. Ptak, S. Johnston, C. Kramer, M. Young, D. Friedman, J. Geisz, W. McMahon, A. Kibbler, J. Olson, R. Crandall, and H. Branz					5d. PROJECT NUMBER NREL/CP-520-38998	
					5e. TASK NUMBER PVA6.4401	
					5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) National Renewable Energy Laboratory 1617 Cole Blvd. Golden, CO 80401-3393					8. PERFORMING ORGANIZATION REPORT NUMBER NREL/CP-520-38998	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)					10. SPONSOR/MONITOR'S ACRONYM(S) NREL	
					11. SPONSORING/MONITORING AGENCY REPORT NUMBER	
12. DISTRIBUTION AVAILABILITY STATEMENT National Technical Information Service U.S. Department of Commerce 5285 Port Royal Road Springfield, VA 22161						
13. SUPPLEMENTARY NOTES						
14. ABSTRACT (Maximum 200 Words) Dilute nitride alloys provide a powerful tool for engineering the band gap and lattice constant of III-V alloys. However, nitrogen degrades the performance of GaAs solar cells. This project seeks to understand and demonstrate the limits of performance of GaInNAs alloys by (a) correlating deep-level transient spectroscopy (DLTS) data with device performance and (b) using molecular beam epitaxy (MBE) to reduce background impurity concentrations.						
15. SUBJECT TERMS Photovoltaics; solar; dilute nitride alloys; PV; NREL						
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT UL	18. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON	
a. REPORT Unclassified	b. ABSTRACT Unclassified	c. THIS PAGE Unclassified			19b. TELEPHONE NUMBER (Include area code)	